

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368


Editors: W.T.A. Harrison, J. Simpson and  
M. Weil

## $\text{Na}_4\text{Fe}^{2+}\text{Fe}^{3+}(\text{PO}_4)_3$ , a new synthetic NASICON-type phosphate

Frédéric Hatert

*Acta Cryst.* (2009). E65, i30

This open-access article is distributed under the terms of the Creative Commons Attribution Licence <http://creativecommons.org/licenses/by/2.0/uk/legalcode>, which permits unrestricted use, distribution, and reproduction in any medium, provided the original authors and source are cited.

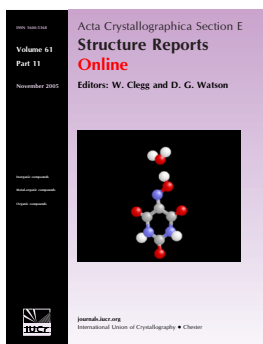

*Acta Crystallographica Section E: Structure Reports Online* is the IUCr's highly popular open-access structural journal. It provides a simple and easily accessible publication mechanism for the growing number of inorganic, metal-organic and organic crystal structure determinations. The electronic submission, validation, refereeing and publication facilities of the journal ensure very rapid and high-quality publication, whilst key indicators and validation reports provide measures of structural reliability. In 2007, the journal published over 5000 structures. The average publication time is less than one month.

Crystallography Journals **Online** is available from [journals.iucr.org](http://journals.iucr.org)

## Na<sub>4</sub>Fe<sup>2+</sup>Fe<sup>3+</sup>(PO<sub>4</sub>)<sub>3</sub>, a new synthetic NASICON-type phosphate

Frédéric Hatert

 University of Liège, Laboratory of Mineralogy B.18, B-4000 Liège, Belgium  
 Correspondence e-mail: fhatert@ulg.ac.be

Received 25 February 2009; accepted 12 March 2009

 Key indicators: single-crystal X-ray study;  $T = 293$  K; mean  $\sigma(\text{P-O}) = 0.008$  Å;  $R$  factor = 0.052;  $wR$  factor = 0.125; data-to-parameter ratio = 8.4.

This paper reports the crystal structure of tetrasodium diiron tris(phosphate), Na<sub>4</sub>Fe<sup>2+</sup>Fe<sup>3+</sup>(PO<sub>4</sub>)<sub>3</sub>, which has been synthesized hydrothermally at 773 K and 0.1 GPa. The crystal structure has been refined in the space group  $R\bar{3}c$  and is identical to that of  $\gamma$ -NASICON. The heteropolyhedral framework is based on a regular alternation, in three dimensions, of corner-sharing PO<sub>4</sub> tetrahedra and FeO<sub>6</sub> octahedra, constituting so-called ‘lantern units’ stacked along the  $c$  axis. The Na<sup>+</sup> cations are distributed over two crystallographic sites: the six-coordinated Na1 site which lies between two ‘lantern units’, and the eight-coordinated Na2 site which lies at the same  $z$  value as the P site.

### Related literature

For general background, see: Hatert *et al.* (2006); Hatert & Fransolet (2006); Hatert (2007*a,b*). For related structures, see: Sljukic *et al.* (1969); Masquelier *et al.* (2000). For bond-valence calculations, see: Brown & Altermatt (1985). For the use of the pressure vessel, see: Tuttle (1949). For the standard used in the chemical analysis, see: Fransolet (1975). For software used to establish the space group, see: Le Page (1987).

### Experimental

#### Crystal data

Na <sub>4</sub> Fe <sub>2</sub> (PO <sub>4</sub> ) <sub>3</sub>	$Z = 6$
$M_r = 488.57$	Mo $K\alpha$ radiation
Trigonal, $R\bar{3}c$	$\mu = 3.68$ mm <sup>-1</sup>
$a = 8.9543$ (9) Å	$T = 293$ K
$c = 21.280$ (4) Å	$0.08 \times 0.05 \times 0.03$ mm
$V = 1477.6$ (4) Å <sup>3</sup>	

#### Data collection

Bruker <i>P4</i> diffractometer	284 reflections with $I > 2\sigma(I)$
Absorption correction: $\psi$ scan ( <i>XSCANS</i> ; Siemens, 1991)	$R_{\text{int}} = 0.021$
$T_{\text{min}} = 0.693$ , $T_{\text{max}} = 0.896$	3 standard reflections
721 measured reflections	every 97 reflections
294 independent reflections	intensity decay: 1.9%

#### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.052$	35 parameters
$wR(F^2) = 0.125$	$\Delta\rho_{\text{max}} = 1.70$ e Å <sup>-3</sup>
$S = 1.40$	$\Delta\rho_{\text{min}} = -0.97$ e Å <sup>-3</sup>
294 reflections	

Data collection: *XSCANS* (Siemens, 1991); cell refinement: *XSCANS*; data reduction: *SHELXTL-Plus* (Sheldrick, 2008); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ATOMS* (Dowty, 1993); software used to prepare material for publication: *SHELXTL-Plus*.

Many thanks are due to A.-M. Fransolet for his constructive comments on the first version of this manuscript and to H.-J. Bernhardt, Ruhr-Universität Bochum, Germany, for the chemical analysis. The author also thanks the FRS–FNRS (Belgium) for a position as ‘Chercheur qualifié’ and for grant Nos. 1.5.113.05.F and 1.5.098.06.F, as well as the Alexander von Humboldt Foundation (Germany) for a research fellowship at the Ruhr-Universität Bochum during the 2004–2005 academic year.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: MG2067).

### References

- Brown, I. D. & Altermatt, D. (1985). *Acta Cryst.* **B41**, 244–247.  
 Dowty, E. (1993). *ATOMS for Windows*. Shape Software, Kingsport, Tennessee, USA.  
 Fransolet, A.-M. (1975). PhD thesis, University of Liège, Belgium.  
 Hatert, F. (2007*a*). *Z. Kristallogr. New Cryst. Struct.* **221**, 1–2.  
 Hatert, F. (2007*b*). 24th European Crystallographic Meeting (ECM-24). Abstract Book, p. s31.  
 Hatert, F. & Fransolet, A.-M. (2006). *Ber. Dtsch. Mineral. Ges. Beih. Eur. J. Mineral.* **18**, 53.  
 Hatert, F., Fransolet, A.-M. & Maresch, W. V. (2006). *Contrib. Mineral. Petrol.* **152**, 399–419.  
 Le Page, Y. (1987). *J. Appl. Cryst.* **20**, 264–269.  
 Masquelier, C., Wurm, C., Rodríguez-Carvajal, J., Gaubicher, J. & Nazari, L. (2000). *Chem. Mater.* **12**, 525–532.  
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.  
 Siemens (1991). *XSCANS*. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.  
 Sljukic, M., Matkovic, B., Prodic, B. & Anderson, D. (1969). *Z. Kristallogr.* **130**, 148–161.  
 Tuttle, O. F. (1949). *Geol. Soc. Am. Bull.* **60**, 1727–1729.

## **supplementary materials**

*Acta Cryst.* (2009). E65, i30 [ doi:10.1107/S1600536809009210 ]

## $\text{Na}_4\text{Fe}^{2+}\text{Fe}^{3+}(\text{PO}_4)_3$ , a new synthetic NASICON-type phosphate

F. Hatert

### Comment

In the natural geological environment of granitic pegmatites, Na–Fe–Mn-bearing phosphates play important geochemical and petrological roles. The alluaudite group of minerals, with an idealized chemical composition  $\text{Na}_2(\text{Mn},\text{Fe}^{2+})_2\text{Fe}^{3+}(\text{PO}_4)_3$ , constitutes a good example of primary phosphates which can be used as geothermometer, or to constrain the oxygen fugacity which prevailed in granitic pegmatites (Hatert *et al.*, 2006). In order to better understand the crystallization conditions of iron-rich alluaudites in pegmatites, we decided to investigate the Na–Fe<sup>2+</sup>–Fe<sup>3+</sup> (+PO<sub>4</sub>) ternary system by hydrothermal methods (Hatert & Fransolet, 2006). These experiments produced several new phosphates, which crystallized in the Na-rich part of the system and were investigated by single-crystal X-ray diffraction techniques (Hatert, 2007*a,b*). Starting from the composition  $\text{Na}_4\text{Fe}^{2+}\text{Fe}^{3+}(\text{PO}_4)_3$ , the hydrothermal synthesis at 500°C and 0.1 GPa produced large pink crystals; their crystal structure is reported herein.

The crystal structure of the title compound has been refined in space group  $R\bar{3}c$  and corresponds to that of centrosymmetric  $\gamma$ -NASICON-type phosphates (Sljukic *et al.*, 1969; Masquelier *et al.*, 2000). The heteropolyhedral framework is based on the regular alternation, in the three dimensions, of corner-sharing PO<sub>4</sub> tetrahedra (P—O = 1.533–1.538 Å) and FeO<sub>6</sub> octahedra (Fe—O = 2.010–2.130 Å; Fig. 1), and shows the stacking, along the *c* direction, of the so-called 'lantern units' (Masquelier *et al.*, 2000). The monovalent Na<sup>+</sup> cations are distributed over two crystallographic sites: the 6-coordinated Na1 site (Na1—O = 2.402 Å) which lies between two 'lantern units', and the 8-coordinated Na2 site (Na2—O = 2.487–2.990 Å) which lies at the same *z* value as the P atom (Fig. 2).

Bond-valence sums were calculated for each ion using the parameters of Brown & Altermatt (1985). The P1 bond-valence sum is 4.99, and the O-atom bond-valence sums are within the normal acceptable range (1.93–2.10). The bond-valence sums also confirm that the Na1 and Na2 sites are filled by Na (0.98–1.19), and that the Fe1 site contains an equal amount of Fe<sup>2+</sup> and Fe<sup>3+</sup> (2.54).

A comparison with the crystal structure of  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> (Masquelier *et al.*, 2000) shows that the two phosphates are isostructural. However, the amount of Na in the title compound reaches 4 atoms per formula unit, and is higher than the Na-content of any other known NASICON-type phosphate. This high Na-content is necessary to maintain charge balance, since the Fe1 site is occupied by 50% Fe<sup>2+</sup> and 50% Fe<sup>3+</sup>. Na atoms are located on the same positions as in  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub>, but the two Na1 and Na2 sites are completely filled by Na atoms in the title compound, whereas their occupancy factors are 0.85 (3) (Na1) and 0.72 (3) (Na2) in  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> (Masquelier *et al.*, 2000).

Masquelier *et al.* (2000) demonstrated that the size of the Na1 cavity is increased as this site is depopulated, and that this increase has a direct influence on the value of the *c* unit-cell parameter. This hypothesis is corroborated by our structural data, which show that a full occupancy of the Na1 site in  $\text{Na}_4\text{Fe}^{2+}\text{Fe}^{3+}(\text{PO}_4)_3$  induces small values for the Na1—O distances

## supplementary materials

and for the  $c$  parameter (2.402 and 21.280 Å, respectively), while a partial occupancy of this site in  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> induces larger values for these parameters (2.500 and 21.808 Å, respectively; Masquelier *et al.*, 2000). The presence of significant amounts of Fe<sup>2+</sup> in the Fe1 site of the title compound also induces a significant increase of the Fe1—O average bond length (2.070 Å), when compared to the Fe1—O bond length reported for  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> (2.002 Å; Masquelier *et al.*, 2000). This increase does not affect the  $c$  unit-cell parameter, but induces a significant increase of the  $a$  parameter, from 8.727 Å in  $\gamma$ -Na<sub>3</sub>Fe<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> (Masquelier *et al.*, 2000), to 8.954 Å in the title compound.

### Experimental

The title compound was synthesized under hydrothermal conditions. The starting material was prepared by mixing NaH<sub>2</sub>PO<sub>4</sub>·H<sub>2</sub>O, Na<sub>2</sub>HPO<sub>4</sub>·2H<sub>2</sub>O, FeO and Fe<sub>2</sub>O<sub>3</sub> in proportions 2:1:1:1/2. About 25 mg of the homogenized mixture was sealed into a gold tube with an outer diameter of 2 mm and a length of 25 mm, containing 2 mg of distilled water. The gold capsule was then inserted in a Tuttle-type pressure vessel (Tuttle, 1949) and maintained at a temperature of 500°C and a pressure of 0.1 GPa. After 3 d, the sample still in the gold tube in the autoclave, was quenched to room temperature in a stream of cold air. The synthesized phosphates consisted of large pink crystals of the title compound, associated with colourless crystals of maricite, NaFe<sup>2+</sup>(PO<sub>4</sub>), and with isometric black crystals of Na<sub>7</sub>Fe<sub>4</sub>(PO<sub>4</sub>)<sub>6</sub>.

A chemical analysis of the title compound has been performed with a CAMEBAX SX-50 electron microprobe (15 kV acceleration voltage, 20 nA beam current, analyst H.-J. Bernhardt, Ruhr-Universität Bochum, Germany). The standards used were graffonite from Kabira (sample KF16; Fransolet, 1975) (Fe, P), and jadeite (Na). The average of 6 point analyses gives P<sub>2</sub>O<sub>5</sub> 42.47, FeO\* 16.94, Fe<sub>2</sub>O<sub>3</sub>\* 14.17, Na<sub>2</sub>O 24.47, total 98.05 wt. % (\* values calculated to maintain charge balance). The chemical composition, calculated on the basis of 3 P, corresponds to Na<sub>3.96</sub>Fe<sup>2+</sup><sub>1.18</sub>Fe<sup>3+</sup><sub>0.89</sub>(PO<sub>4</sub>)<sub>3</sub>.

### Refinement

A first refinement in space group  $R\bar{3}$  converged to a satisfactory model with  $R_1 = 0.0328$ , but a check of these structural data with the program ADDSYM (Le Page, 1987) immediately allowed to identify supplementary symmetry elements, thus confirming the space group  $R\bar{3}c$ . All atoms were refined anisotropically, and a preliminary refinement of the site occupancy factors of Na1 and Na2 confirmed that these sites were filled with Na atoms only. In the final refinement cycle, the Na1 and Na2 site occupancy factors were consequently constrained to 1.0.

### Figures

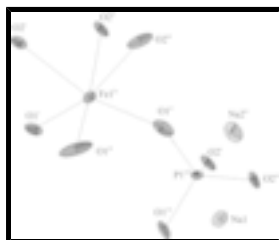


Fig. 1. Fragment of the Na<sub>4</sub>Fe<sup>2+</sup>Fe<sup>3+</sup>(PO<sub>4</sub>)<sub>3</sub> structure (50% displacement ellipsoids) showing the bonding environments of the Fe and P cations. [Symmetry codes: (i) 2/3 + x - y, 1/3 - y, 1/3 - z; (ii) 2/3 - x, 1/3 - x + y, 1/3 - z; (iii) 2/3 + y, 1/3 + x, 1/3 - z; (iv) x, -y - 1/3, z; (v) x, x - y, 1/6 - z; (vi) 1/3 + y, 2/3 - x + y, 1/6 - z; (vii) 2/3 - y, 1/3 + x - y, z - 1/6; (viii) -y, -x, z; (ix) x + 2/3, y + 1/3, 1/3 - z.]

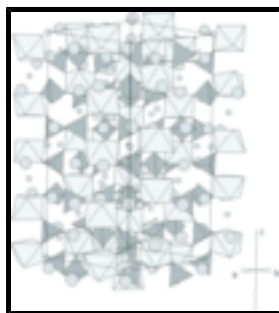


Fig. 2. Polyhedral view of the  $\text{Na}_4\text{Fe}^{2+}\text{Fe}^{3+}(\text{PO}_4)_3$  structure.  $\text{FeO}_6$  octahedra are shown with light shading,  $\text{PO}_4$  tetrahedra with dark shading, Na1 as small circles, and Na2 as large circles.

### Tetrasodium diiron tris(phosphate)

#### Crystal data

$\text{Na}_{3.96}\text{Fe}_{2.07}(\text{PO}_4)_3$

$M_r = 488.57$

Trigonal,  $R\bar{3}c$

Hall symbol:  $-R\ 3\ 2''c$

$a = 8.9543\ (9)\ \text{\AA}$

$b = 8.9543\ (9)\ \text{\AA}$

$c = 21.280\ (4)\ \text{\AA}$

$\alpha = 90^\circ$

$\beta = 90^\circ$

$\gamma = 120^\circ$

$V = 1477.6\ (4)\ \text{\AA}^3$

$Z = 6$

$F_{000} = 1422$

$D_x = 3.294\ \text{Mg m}^{-3}$

Mo  $K\alpha$  radiation

$\lambda = 0.71073\ \text{\AA}$

Cell parameters from 35 reflections

$\theta = 5.9\text{--}12.6^\circ$

$\mu = 3.68\ \text{mm}^{-1}$

$T = 293\ \text{K}$

Isometric crystal, pink

$0.08 \times 0.05 \times 0.03\ \text{mm}$

#### Data collection

Bruker P4  
diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 293\ \text{K}$

$P = 100\ \text{kPa}$

$\omega$  scans

Absorption correction:  $\psi$  scan  
(XSCANS; Siemens, 1991)

$T_{\min} = 0.693$ ,  $T_{\max} = 0.896$

721 measured reflections

294 independent reflections

284 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.021$

$\theta_{\max} = 25.0^\circ$

$\theta_{\min} = 3.3^\circ$

$h = -10 \rightarrow 1$

$k = -1 \rightarrow 10$

$l = -25 \rightarrow 1$

3 standard reflections

every 97 reflections

intensity decay: 1.9%

#### Refinement

Refinement on  $F^2$

Least-squares matrix: full

Secondary atom site location: difference Fourier map

$$w = 1/[\sigma^2(F_o^2) + (0.0415P)^2 + 5P]$$

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

# supplementary materials

$R[F^2 > 2\sigma(F^2)] = 0.052$	$(\Delta/\sigma)_{\max} < 0.001$
$wR(F^2) = 0.125$	$\Delta\rho_{\max} = 1.70 \text{ e } \text{\AA}^{-3}$
$S = 1.40$	$\Delta\rho_{\min} = -0.97 \text{ e } \text{\AA}^{-3}$
294 reflections	Extinction correction: SHELXL97 (Sheldrick, 2008), $F_c^* = kFc[1+0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$
35 parameters	Extinction coefficient: 0.0027 (6)
Primary atom site location: structure-invariant direct methods	

## Special details

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

## Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )

	$x$	$y$	$z$	$U_{\text{iso}}^*/U_{\text{eq}}$
Fe1	0.0000	0.0000	0.14926 (9)	0.0082 (8)
P1	-0.3333	-0.3672 (3)	0.0833	0.0080 (9)
Na1	0.0000	0.0000	0.0000	0.0129 (17)
Na2	-0.3333	-0.0278 (7)	0.0833	0.0262 (13)
O1	0.1950 (8)	0.2066 (9)	0.1913 (3)	0.0213 (15)
O2	0.1869 (8)	0.0152 (7)	0.0838 (3)	0.0135 (14)

## Atomic displacement parameters ( $\text{\AA}^2$ )

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Fe1	0.0070 (8)	0.0070 (8)	0.0105 (11)	0.0035 (4)	0.000	0.000
P1	0.0041 (15)	0.0109 (12)	0.0065 (14)	0.0021 (7)	0.0000 (10)	0.0000 (5)
Na1	0.009 (2)	0.009 (2)	0.020 (4)	0.0047 (12)	0.000	0.000
Na2	0.013 (3)	0.029 (2)	0.031 (3)	0.0065 (13)	-0.001 (2)	-0.0005 (11)
O1	0.015 (3)	0.032 (4)	0.013 (3)	0.008 (3)	-0.006 (2)	-0.008 (3)
O2	0.012 (3)	0.019 (3)	0.012 (3)	0.010 (3)	-0.004 (2)	-0.006 (2)

## Geometric parameters ( $\text{\AA}$ , $^\circ$ )

Fe1—O1	2.010 (6)	Na1—O2 <sup>vii</sup>	2.402 (5)
Fe1—O1 <sup>i</sup>	2.010 (6)	Na1—O2 <sup>i</sup>	2.402 (5)
Fe1—O1 <sup>ii</sup>	2.010 (6)	Na1—O2 <sup>ii</sup>	2.402 (5)
Fe1—O2 <sup>i</sup>	2.130 (6)	Na1—O2 <sup>viii</sup>	2.402 (5)

Fe1—O2	2.130 (6)	Na2—O2 <sup>i</sup>	2.487 (8)
Fe1—O2 <sup>ii</sup>	2.130 (6)	Na2—O2 <sup>v</sup>	2.487 (8)
P1—O1 <sup>iii</sup>	1.533 (6)	Na2—O2 <sup>ii</sup>	2.493 (6)
P1—O1 <sup>iv</sup>	1.533 (6)	Na2—O2 <sup>ix</sup>	2.493 (6)
P1—O2 <sup>i</sup>	1.538 (6)	Na2—O1 <sup>ix</sup>	2.534 (6)
P1—O2 <sup>v</sup>	1.538 (6)	Na2—O1 <sup>ii</sup>	2.534 (6)
Na1—O2 <sup>vi</sup>	2.402 (5)	Na2—O1 <sup>x</sup>	2.990 (8)
Na1—O2	2.402 (5)	Na2—O1 <sup>xi</sup>	2.990 (8)
O1—Fe1—O1 <sup>i</sup>	101.7 (2)	O2—Na1—O2 <sup>viii</sup>	109.0 (2)
O1—Fe1—O1 <sup>ii</sup>	101.7 (2)	O2 <sup>vii</sup> —Na1—O2 <sup>viii</sup>	71.0 (2)
O1 <sup>i</sup> —Fe1—O1 <sup>ii</sup>	101.7 (2)	O2 <sup>i</sup> —Na1—O2 <sup>viii</sup>	180.00 (17)
O1—Fe1—O2 <sup>i</sup>	165.5 (2)	O2 <sup>ii</sup> —Na1—O2 <sup>viii</sup>	109.0 (2)
O1 <sup>i</sup> —Fe1—O2 <sup>ii</sup>	86.5 (2)	O2 <sup>i</sup> —Na2—O2 <sup>v</sup>	60.5 (3)
O1 <sup>ii</sup> —Fe1—O2 <sup>i</sup>	88.1 (2)	O2 <sup>i</sup> —Na2—O2 <sup>ii</sup>	68.1 (3)
O1—Fe1—O2	86.5 (2)	O2 <sup>v</sup> —Na2—O2 <sup>ii</sup>	128.6 (2)
O1 <sup>i</sup> —Fe1—O2	88.1 (2)	O2 <sup>i</sup> —Na2—O2 <sup>ix</sup>	128.6 (2)
O1 <sup>ii</sup> —Fe1—O2	165.5 (2)	O2 <sup>v</sup> —Na2—O2 <sup>ix</sup>	68.1 (3)
O2 <sup>i</sup> —Fe1—O2	81.8 (2)	O2 <sup>ii</sup> —Na2—O2 <sup>ix</sup>	163.3 (4)
O1—Fe1—O2 <sup>ii</sup>	88.1 (2)	O2 <sup>i</sup> —Na2—O1 <sup>ix</sup>	93.1 (2)
O1 <sup>i</sup> —Fe1—O2 <sup>ii</sup>	165.5 (2)	O2 <sup>v</sup> —Na2—O1 <sup>ix</sup>	70.0 (2)
O1 <sup>ii</sup> —Fe1—O2 <sup>ii</sup>	86.5 (2)	O2 <sup>ii</sup> —Na2—O1 <sup>ix</sup>	114.28 (19)
O2 <sup>i</sup> —Fe1—O2 <sup>ii</sup>	81.8 (2)	O2 <sup>ix</sup> —Na2—O1 <sup>ix</sup>	68.73 (19)
O2—Fe1—O2 <sup>ii</sup>	81.8 (2)	O2 <sup>i</sup> —Na2—O1 <sup>ii</sup>	70.0 (2)
O1 <sup>iii</sup> —P1—O1 <sup>iv</sup>	109.6 (5)	O2 <sup>v</sup> —Na2—O1 <sup>ii</sup>	93.1 (2)
O1 <sup>iii</sup> —P1—O2 <sup>i</sup>	106.9 (3)	O2 <sup>ii</sup> —Na2—O1 <sup>ii</sup>	68.73 (19)
O1 <sup>iv</sup> —P1—O2 <sup>i</sup>	112.1 (3)	O2 <sup>ix</sup> —Na2—O1 <sup>ii</sup>	114.28 (19)
O1 <sup>iii</sup> —P1—O2 <sup>v</sup>	112.1 (3)	O1 <sup>ix</sup> —Na2—O1 <sup>ii</sup>	160.8 (4)
O1 <sup>iv</sup> —P1—O2 <sup>v</sup>	106.9 (3)	O2 <sup>i</sup> —Na2—O1 <sup>x</sup>	113.49 (19)
O2 <sup>i</sup> —P1—O2 <sup>v</sup>	109.2 (5)	O2 <sup>v</sup> —Na2—O1 <sup>x</sup>	154.86 (18)
O2 <sup>vi</sup> —Na1—O2	180.0 (3)	O2 <sup>ii</sup> —Na2—O1 <sup>x</sup>	52.52 (18)
O2 <sup>vi</sup> —Na1—O2 <sup>vii</sup>	71.0 (2)	O2 <sup>ix</sup> —Na2—O1 <sup>x</sup>	112.9 (3)
O2—Na1—O2 <sup>vii</sup>	109.0 (2)	O1 <sup>ix</sup> —Na2—O1 <sup>x</sup>	86.74 (13)
O2 <sup>vi</sup> —Na1—O2 <sup>i</sup>	109.0 (2)	O1 <sup>ii</sup> —Na2—O1 <sup>x</sup>	108.0 (2)
O2—Na1—O2 <sup>i</sup>	71.0 (2)	O2 <sup>i</sup> —Na2—O1 <sup>xi</sup>	154.86 (18)
O2 <sup>vii</sup> —Na1—O2 <sup>i</sup>	109.0 (2)	O2 <sup>v</sup> —Na2—O1 <sup>xi</sup>	113.49 (19)
O2 <sup>vi</sup> —Na1—O2 <sup>ii</sup>	109.0 (2)	O2 <sup>ii</sup> —Na2—O1 <sup>xi</sup>	112.9 (3)
O2—Na1—O2 <sup>ii</sup>	71.0 (2)	O2 <sup>ix</sup> —Na2—O1 <sup>xi</sup>	52.52 (18)
O2 <sup>vii</sup> —Na1—O2 <sup>ii</sup>	180.0 (3)	O1 <sup>ix</sup> —Na2—O1 <sup>xi</sup>	108.0 (2)
O2 <sup>i</sup> —Na1—O2 <sup>ii</sup>	71.0 (2)	O1 <sup>ii</sup> —Na2—O1 <sup>xi</sup>	86.74 (13)
O2 <sup>vi</sup> —Na1—O2 <sup>viii</sup>	71.0 (2)	O1 <sup>x</sup> —Na2—O1 <sup>xi</sup>	82.0 (3)



## supplementary materials

Symmetry codes: (i)  $-x+y, -x, z$ ; (ii)  $-y, x-y, z$ ; (iii)  $-x+y-1/3, y-2/3, z-1/6$ ; (iv)  $x-y-1/3, x-2/3, -z+1/3$ ; (v)  $x-y-2/3, -y-1/3, -z+1/6$ ; (vi)  $-x, -y, -z$ ; (vii)  $y, -x+y, -z$ ; (viii)  $x-y, x, -z$ ; (ix)  $y-2/3, x-1/3, -z+1/6$ ; (x)  $x-1/3, x-y+1/3, z-1/6$ ; (xi)  $-x-1/3, -y+1/3, -z+1/3$ .

Fig. 1

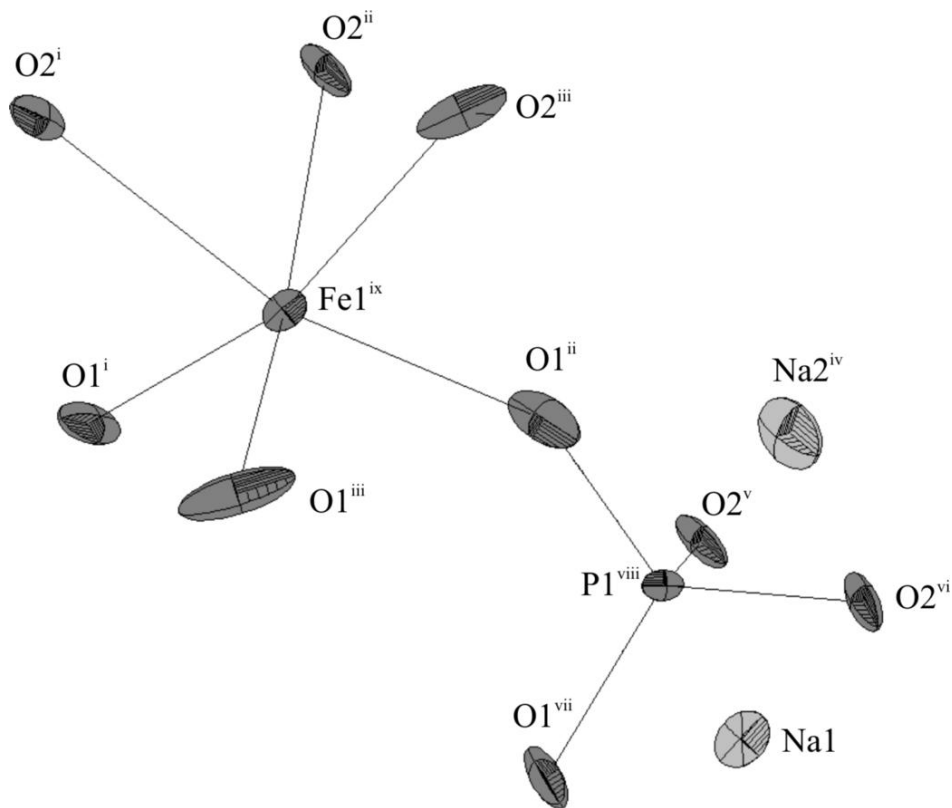


Fig. 2

