



# Dispersion Nitroxide Mediated Polymerization of MMA in Supercritical Carbon Dioxide

Grignard Bruno<sup>1</sup>, Gigmès Didier<sup>2</sup>, Jérôme Christine<sup>1</sup>, Detrembleur Christophe<sup>1</sup>


1) CERM, University of Liège, Sart-Tilman, B6a, B-4000 Liège, Belgium

2) UMR 6264 - Laboratoire Chimie Provence


Universités d'Aix-Marseille 1, 2 et 3-Case 542 Av. Escadrille Normandie Niemen  
13397 Marseille Cedex 20, France

**1. Introduction.** Nitroxide Mediated Polymerization is a very attractive metal-free controlled radical process that allows the polymerization of a broad range of monomers, including the functional ones. In NMP, a relatively weak C-ON bond is homolytically and reversibly cleaved under thermal stimuli to generate a growing radical (active species) and a less reactive radical also known as persistent or stable free radical (nitroxide). Until now, NMP in organic solvents or water as polymerization medium was extensively studied. In this contribution, we would like to report on the first **dispersion NMP of MMA in an environmentally friendly medium, i.e. supercritical carbon dioxide** using CO<sub>2</sub>-philic perfluorinated polymers as precursors of the stabilizer that was generated "in situ" during the MMA polymerization.

**2. Strategy.** The control of the MMA polymerization relies on the strategy developed by Charleux et al. that consists of using a SG1-based alkoxyamine, i.e. the blocbuilder, in the presence of small amount of styrene. In a first step, CO<sub>2</sub> soluble polyheptafluorodecylacrylate was prepared by homogeneous NMP in scCO<sub>2</sub> using blocbuilder as an alkoxyamine. In a second step, nitroxide SG1 mediated dispersion polymerization of MMA was conducted at 70°C in the presence of 5 wt% of polyheptafluorodecylacrylate end-capped by SG1.

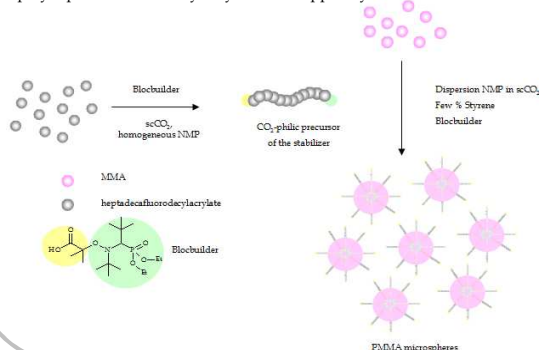


**5. PMMA stabilization.** After depressurisation of the cell, PMMA was collected as a free flowing powder. Depending on the molecular weight of PMMA prepared by dispersion NMP, ill-stabilized particles (A), well defined microspheres with an average diameter of 91 +/- 7 µm (C) or microspheres/elongated particles mixtures (B) are produced.

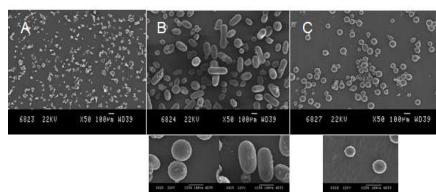

SEM characterization of PMMA particles obtained by dispersion NMP in scCO<sub>2</sub> at 70°C in the presence of 5 wt% of PFDA-SG1 surfactant  
A: PMMA, Mn = 18500 g/mol, PDI = 1.29  
B: PMMA, Mn = 57000 g/mol, PDI = 1.26  
C: PMMA, Mn = 94000 g/mol, PDI = 1.31

**3. Homogeneous NMP of heptafluorodecyl acrylate (FDA) in scCO<sub>2</sub>.** Homogeneous NMP of FDA was conducted at 100°C for 24h at 300 bar in the presence of blocbuilder as alkoxyamine. Livingness of the polymerization was evidenced by the synthesis of PFDA-b-PnBuA diblock copolymer in scCO<sub>2</sub>.

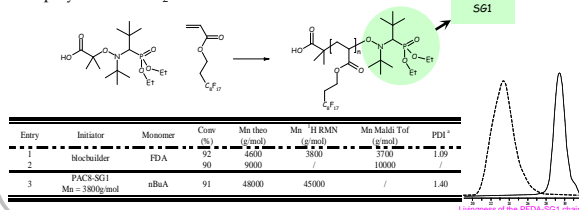


**4. NMP of MMA in scCO<sub>2</sub>; evidence of the control.** NMP of MMA was conducted at 300 bars and 70°C for 114h in the presence of 8.8 mol% of styrene in order to observe control of the polymerisation and 5 wt% of PFDA-SG1 as precursor of the stabilizer that will be generated "in situ". Whatever the MMA/alkoxyamine molar ratio, Mn exp. was in good agreement with Mn theo. and PMMA with narrow polydispersity was produced.


Entry	T (°C)	Time (h)	PFDA-SG1 loading (wt%)	Conv (%) <sup>a</sup>	Mn theo <sup>b</sup> (g/mol)	Mn exp <sup>c</sup> (g/mol)	PDI
1	70	114	5	89	17800	18500	1.29
2	70	114	5	90	90000	94000	1.31
3	70	114	5	98	54000	60000	1.22

Overlay of SEC traces recorded for PMMA prepared by dispersion NMP in scCO<sub>2</sub>.

- PMMA, Mn = 18500 g/mol, PDI = 1.29, entry 2
- PMMA, Mn = 57000 g/mol, PDI = 1.26, entry 1
- PMMA, Mn = 94000 g/mol, PDI = 1.31, entry 3

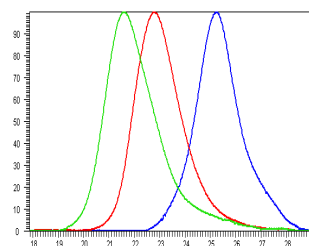

**6. PMMA stabilization: effect of the stabilizer precursor loading.** PFDA-SG1 loading was changed in order to improve the stabilization of PMMA growing particles. A same experiment was then repeated in the previously reported conditions in the presence of 5%, 10% or without precursor of the stabilizer. Without stabilizer, PMMA was collected as a single chunk of polymer whereas powders consisting of microspheres with a mean diameter of 16 +/- 2 µm or microspheres/elongated particles mixtures were obtained in the presence of 10 and 5% of the stabilizer precursor respectively

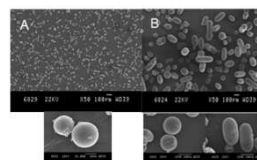

SEM characterization of PMMA particles obtained by dispersion NMP in scCO<sub>2</sub> at 70°C: effect of the surfactant loading  
A: PMMA, Mn = 57000 g/mol, PDI = 1.26, 10 wt% of PFDA-SG1  
B: PMMA, Mn = 60000 g/mol, PDI = 1.22, 5 wt% of PFDA-SG1

**7. Effect of the styrene loading on the polymerization control.** Charleux demonstrated that the control of the NMP of MMA using SG1 based alkoxyamine was due to the presence of a styryl-SG1 moiety at the ω chain-end. So, a decrease of the styrene content was expected to influence the polymerization control. A same experiment was then repeated (70°C, 300 bar, 5wt% of PFDA-SG1) in the presence of decreasing amount of styrene. At higher styrene loading (8.8 or 4.4 mol%), NMP of MMA is controlled whereas at low styrene loading of 2.2% or without styrene, the control is lost.

Entry	T (°C)	Time (h)	PFDA-SG1 loading (wt%)	Styrene loading (%)	Conv (%) <sup>a</sup>	Mn theo <sup>b</sup> (g/mol)	Mn exp <sup>c</sup> (g/mol)	PDI
1	70	114	5	8.8	94	53000	53000	1.25
2	70	114	5	4.4	95	52000	56000	1.26
3	70	114	5	2.2	85	47000	25000	1.55
4	70	114	5	0	91	50000	29000	1.44

**8. Conclusion.** The synthesis of PMMA microspheres by dispersion NMP was successfully achieved in supercritical carbon dioxide using a fluorinated polyacrylate terminated by SG1, prepared by homogeneous NMP in this medium, as precursor of the stabilizer that was generated "in situ". Polymers with well defined molecular weight and narrow polydispersities (Mw/Mn ~1.2) were produced when small amount of styrene were added in the polymerization medium.

**Acknowledgments** The authors are indebted to the "Belgian Science Policy" for general support to CERM in the frame of the "Interuniversity Attraction Poles Programme (IAP 6/27) - Functional Supramolecular Systems". B.G. thanks the "Region Wallonne" and the FEDER for their financial support in the frame of the SINOPLISS project. C.D. thanks the "Fonds National pour la Recherche Scientifique" (FNRS) for financial support. C.D. is maître de recherche.

